

Biodegradable Polymers Derived From Aminoacids


Samuel J. Huang* and Luang-Hua Ho

Polymers and Biosystems Group, Institute of Materials Science, University of Connecticut
Storrs, CT 06269-3136 USA

SUMMARY: Poly(amide-ester)s derived from five α -amino acid mixtures, including glycine, DL- and L-alanines, DL- and L-phenylalanines, and three different diols including 1,6-hexanediol, 1,4-butanediol and *trans*-1,4-cyclohexanedimethanol were synthesized by interfacial, solution and melt polymerizations. All of the polymers had Tg's ranging from -6 to 50°C. The incorporation of rigid *trans*-1,4-cyclohexanedimethanol in the main chain significantly increased the Tg of these polymers. The degree of crystallinity depended on the type of amino acid and decreased with the size of substituent on the α -carbon in the amino acid. Biodegradation of these polymers were tested semi-quantitatively by turbidity measurements. Enzymes used included subtilisin, pronase E, α -chymotrypsin, *fusarium*, and lipase. The incorporation of *trans*-1,4-cyclohexanedimethanol unit slowed down degradation rate. Polymers containing L-amino acid generally degraded faster than the polymers containing DL-amino acids. Quantitative biodegradation testings using ninhydrin analysis, total organic analysis, and weight loss done on alanine derived polymers indicated that the degradation of the polymers by pronase E occurred at the ester bonds first and was specific against L-amino acid. The degradation was followed by slower amide bond degradation.

Introduction

The use of biodegradable polymer in biomedical applications and waste management have increased steady in recent years¹⁻¹⁶. By and large aliphatic polyesters prepared by ring opening polymerization of cyclic lactones, such as glycolide, lactide, and to a much small extent trimethylene carbonate and dioxanone. The advance of the field is seriously material limited. We have directed some of our efforts toward the design, synthesis, characterization and testing of novel biodegradable polymers other than polyesters that are suitable for *in vivo* applications. In order to minimize potential toxicity of polymers and their degradation products we limited our choice of starting materials to natural



$n = 8$



From sebacoyl chloride

$\text{R}' = ((\text{CH}_2)_x, x = 4 \text{ or } 6) \text{ or}$




From diols

$\left. \begin{array}{l} \text{R} = \text{H (Glycine)} \\ \text{or } \text{CH}_3 \text{ (DL \& L-Alanine)} \\ \text{or } \text{CH}_2\text{Ph (DL \& L-Phenylalanine)} \end{array} \right\}$



From amino acids

$\star = \text{Chiral center}$



$\text{Na}_2\text{CO}_3/\text{H}_2\text{O}/\text{CH}$






Figure 1. General Structure of Poly(amide-ester)s and the Sources of the Structural Units

Figure 2. Synthesis of Poly



sebacoyl chloride

From diols

From amino acids

ester)s and the Sources of the

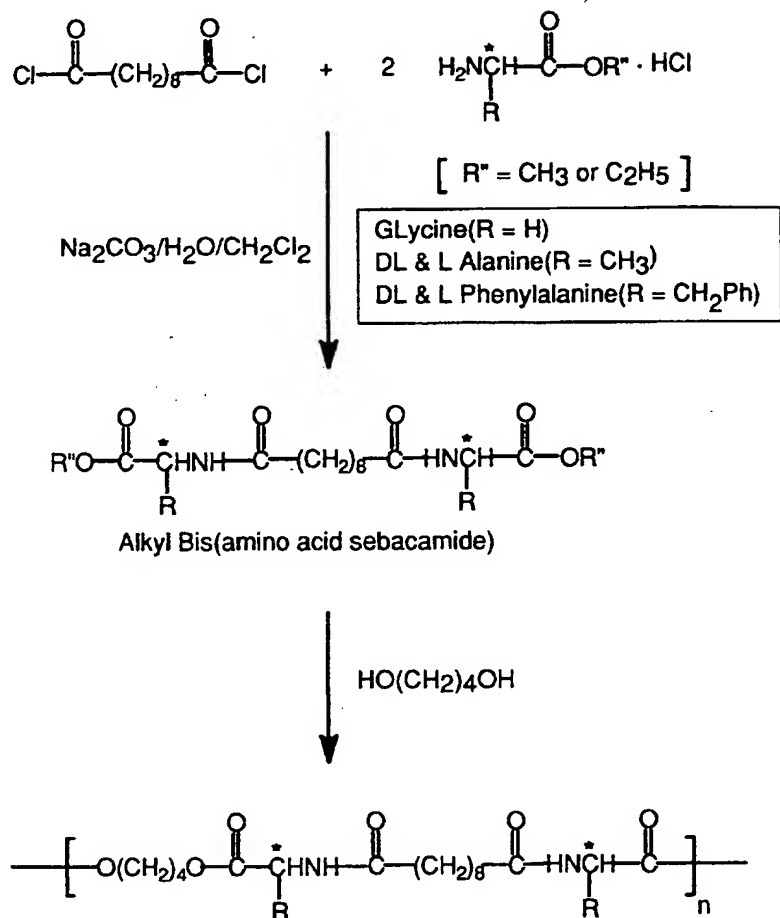


Figure 2. Synthesis of Poly(amide-ester)s by Melt Polymerization

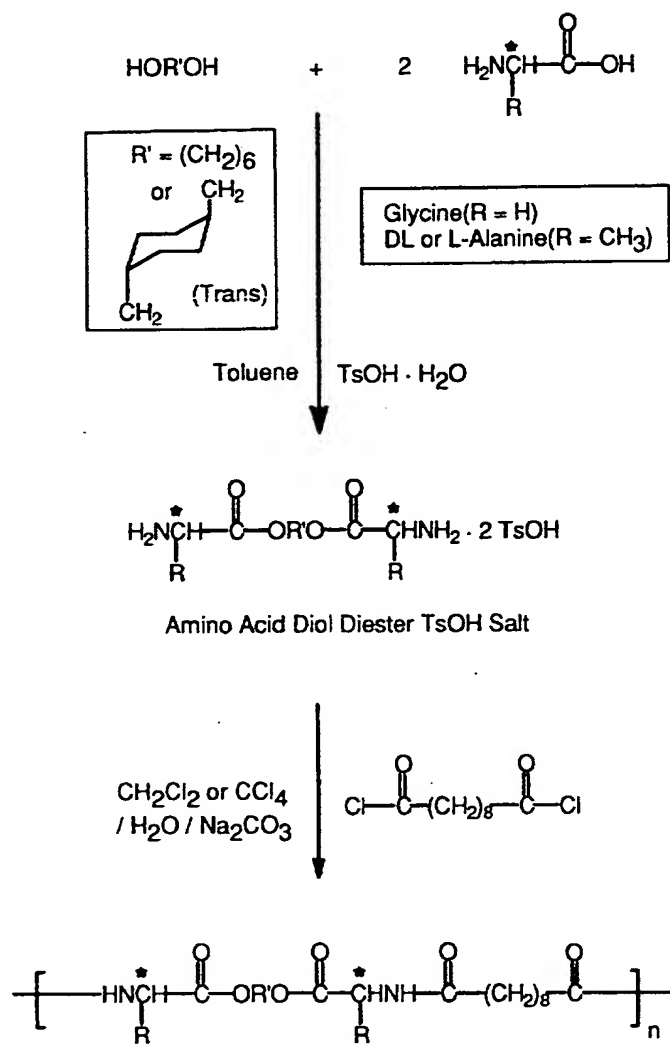



Figure 3. Synthesis of Poly(amide-ester)s by Interfacial Polymerization

H₂I

An








Figure 4. Synthesis of I



Glycine(R = H)
DL or L-Alanine(R = CH₃)



ster TsOH Salt



Interfacial Polymerization

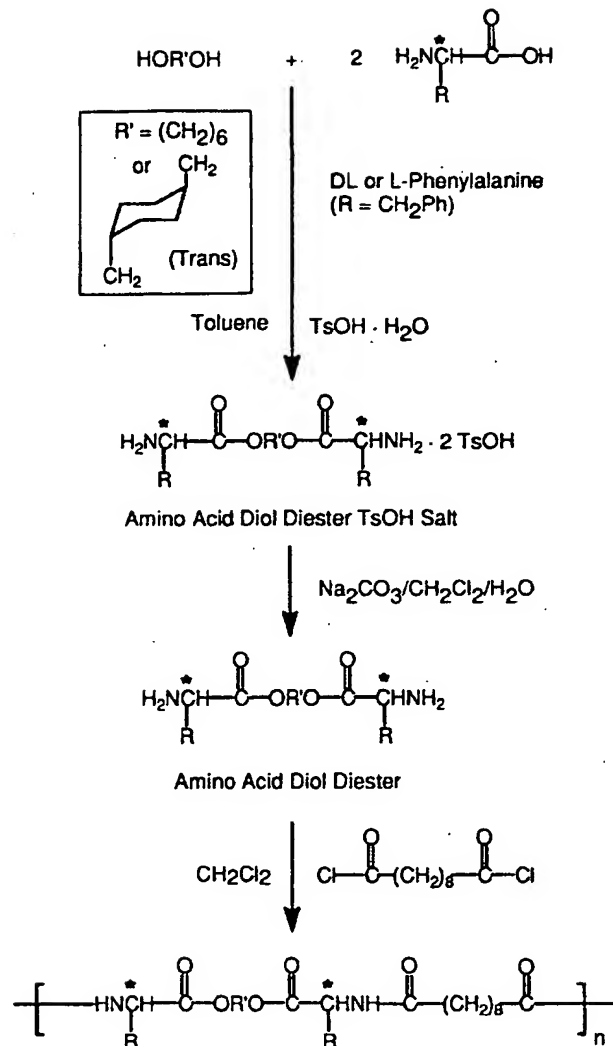


Figure 4. Synthesis of Poly(amide-ester)s by Solution Polymerization

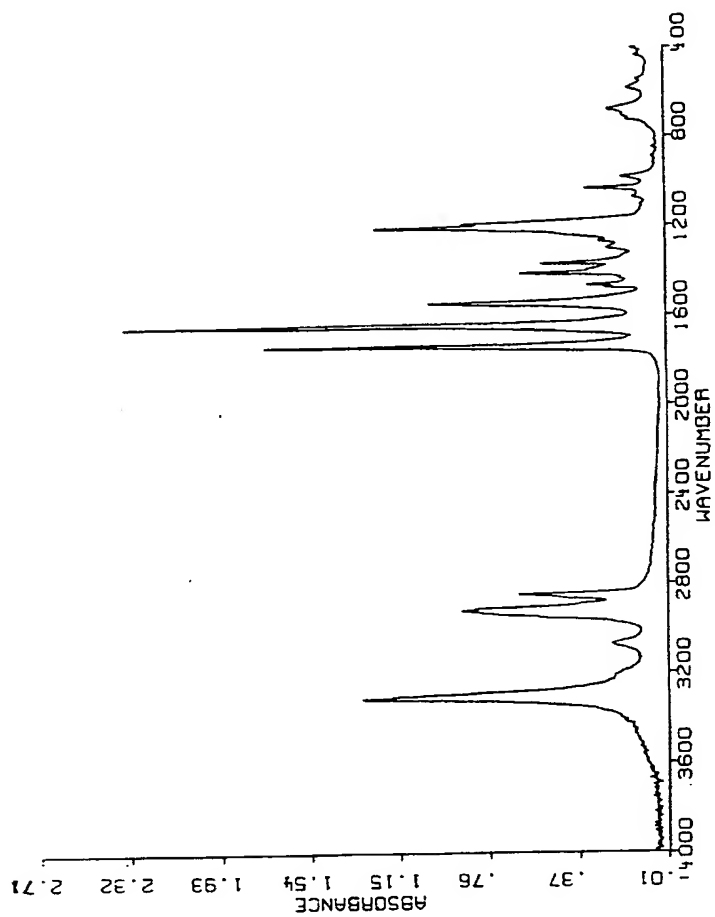


Figure 5. FT-IR Spectrum of GHS Polymer

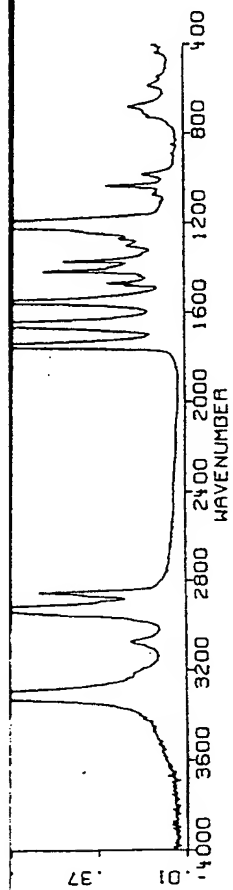


Figure 5. FT-IR Spectrum of GHS Polymer

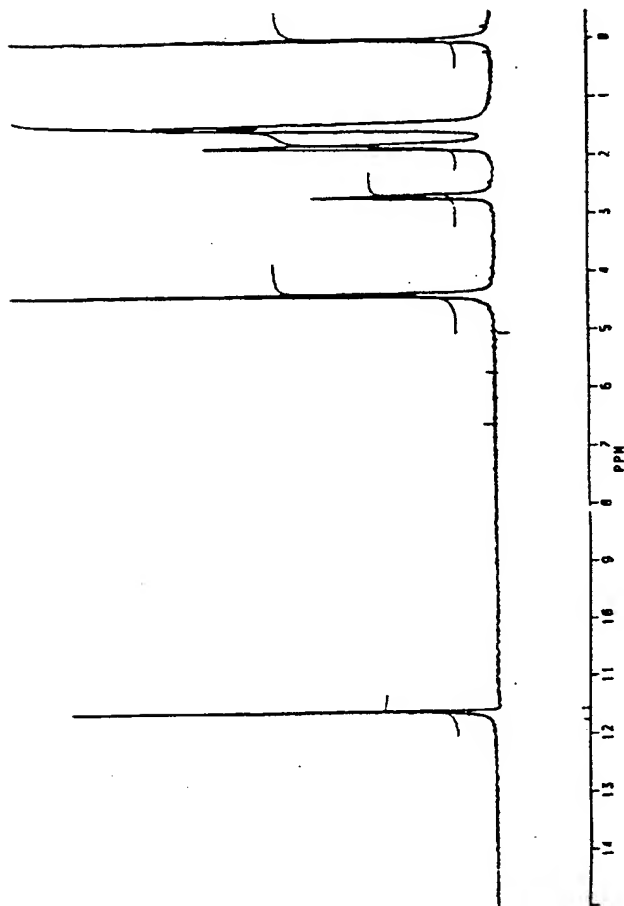


Figure 6. 1H NMR Spectrum of GHS Polymer

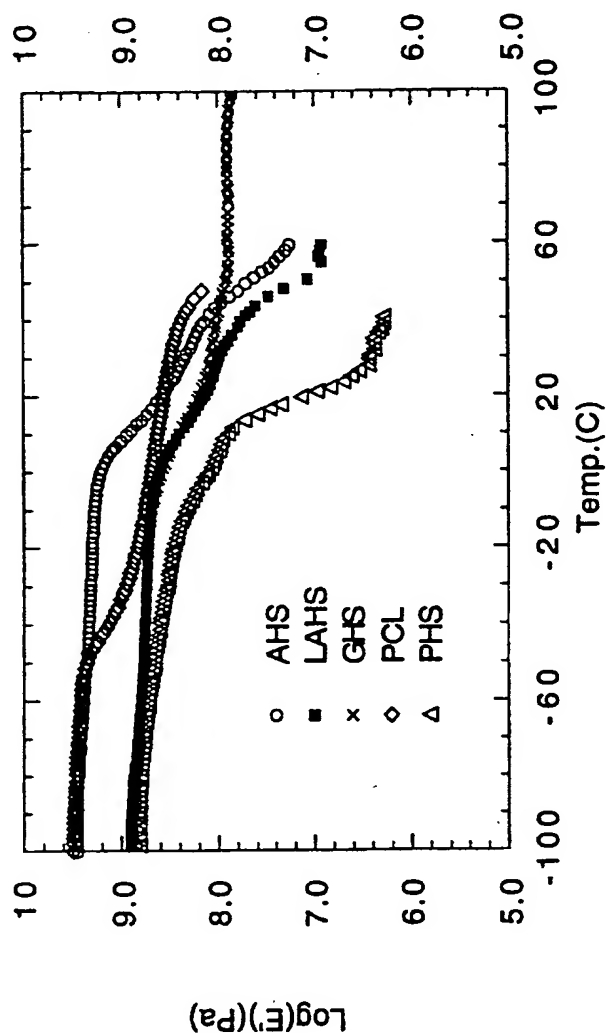


Figure 7. Storage Modulus vs. Temperature Plots for Poly(amide-ester)s as Measured by DMTA

Table 1. Summary

Polymer
Nylon 12/10
Model Polymer 2 ^b
GHS
AHS ^c
LAHS ^c
PHS
LPHS
GCHS
ACHS
LACHS
PCHS
LPCHS
GBS
ABS
LABS
PBS
LPBS
(G-co-P)HS
(G-co-LP)CHS

a: Data in parenthesis quenching; b: Poly(4,9-Data obtained from the 1 was due to the melting of

Figure 7. Storage Modulus vs. Temperature Plots for Poly(amide-ester)s as Measured by DMTA

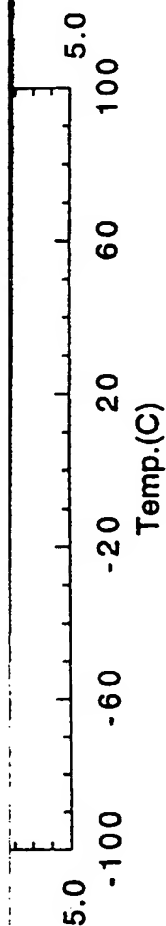


Table 1. Summary of the Thermal Properties of Poly(amide-ester)s


Polymer	$T_m(^{\circ}\text{C})$	$\Delta H_f(\text{J/g})$	$T_g(^{\circ}\text{C})$
Nylon 12/10	197(189&200)	86(72)	---(---)
Model Polymer 2 ^b	156(157)	68(45)	---(---)
GHS	129&142(132&142)	83(49)	---(---)
AHS ^c	40&90(---)	40(---)	---(19)
LAHS ^c	38&86(---)	48(---)	---(8)
PHS	---(---)	---(---)	27(27)
LPHS	---(---)	---(---)	5(5)
GCHS	173(176)	53(53)	---(---)
ACHS	96(---)	36(---)	(50)
LACHS	103&124(---)	35(---)	(47)
PCHS	---(---)	---(---)	49(49)
LPCHS	127&137(---)	30(---)	42(47)
GBS	139&154(135&154)	84(73)	---(---)
ABS	105&112(111)	57(44 ^d)	---(4)
LABS	93&101(---)	56(---)	---(7)
PBS	---(---)	---(---)	8(7)
LPBS	---(---)	---(---)	(-6)
(G-co-P)HS	55(---)	12(---)	(4)
(G-co-LP)CHS	89(---)	16(---)	37(45)

a: Data in parenthesis were obtained from the 2nd heats after quenching; b: Poly(4,9-dioxa-1,12-dodecamethylene sebacamide); c: Data obtained from the polymer annealed at 56°C for 4 days; d: This was due to the melting of the recrystallization of the polymer

products and synthetic compounds that are known to be assimilable by the body. Saccharides, poly saccharides, fatty acids, α -aminoacids, and glycols are among those we have used since they are in general biocompatible. Alpha-aminoacids are of special interest to us and other researchers since they provide a large variety of structural feature that can be incorporated in the polymer chains resulting in a broad spectrum of property and degradability⁷⁻¹¹. As part of our systematic studies of the effect of structural feature on biodegradability we have studied multi-functional group containing polymers¹²⁻¹⁴. We report our recent results on poly(amide-ester)s derived from alpha-aminoacids.

Results and Discussion

Conformational flexibility of polymer chains facilitates biodegradation. As a result aliphatic polyesters are the main group of polymers that are practical biodegradable polymers. Acids are generated during the degradation of polyesters and in cases where surface/volume ratio is small autocatalysis occurs¹⁶. We reasoned that hydrolysis of the amide group of poly(amide-ester)s would produce amines and acids which should act as buffers resulting in less change of pH as compared with polyester hydrolysis. Convenient synthetic procedures were used for the preparation of poly(amide-ester)s including the synthesis of aminoacid glycol diesters and diesters of aminoacid dicarboxylates as monomers; interfacial, solution and melt polymerization to give the poly(amide-ester)s. Structures of the polymers prepared for synthesis are shown in Figures 2-4. These polymers have molecular weight ranging from 10,000-35,000 (by size exclusion chromatography, end group analyses and in some cases, N.M.R.). FTIR, N.M.R. and elemental analyses supported the assigned structures¹⁵. Representative spectra are shown in Figure 5 & 6 for glycine derived poly(amide-ester), GHS. Depending on the substituent and optical composition of the alpha-aminoacids used the resulting polymers are mostly partial crystalline with exception of some polymers derived from phenylalanine, which remain amorphous after aging several months at room temperature, Table 1. The melting points are lower than those of analogous polyamides, Nylon 12, 10 at 197°C, poly(4,9-dioxa-1,12-dodecamethylene sebacamide) at 156°C and GHS at 129 & 142°C. These polymers have the same sebacyl residue but amine residue of different flexibility. Preliminary degradation results also indicate that the rate of degradation increases with flexibility. Interestingly all these polymers are highly crystalline (high ΔH_f) and DSC studies could not detect the Tg's. However, DMTA studies, Figures 7 & 8, do reveal Tg's generally below r.t. as expected due to the ester segments.

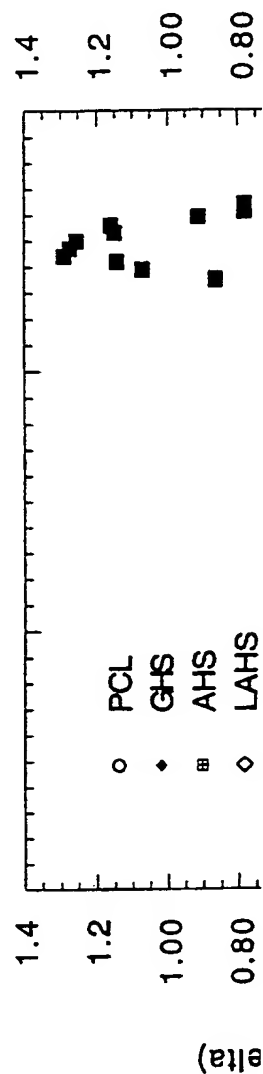

assimilable by the body. Saccharides, poly
among those we have used since they are in
interest to us and other researchers since
can be incorporated in the polymer chains
y⁷⁻¹¹. As part of our systematic studies of
studied multi-functional group containing
le-ester)s derived from alpha-aminoacids.

s biodegradation. As a result aliphatic
tical biodegradable polymers. Acids are
ases where surface/volume ratio is small
amide group of poly(amide-ester)s would
ulting less change of pH as compared with
ere used for the preparation of poly(amide-
s and diesters of aminoacid dicarboxylates
rization to give the poly(amide-ester)s.
own in Figures 2-4. These polymers have
clusion chromatograp, end group analyses
mental analyses supported the assigned
& 6 for glycine derived poly(amide-ester),
osition of the alpha-aminoacids used the
xception of some polymers derived from
eral months at room temperature, Table 1.
amides, Nylon 12, 10 at 197°C, poly(4,9-
HS at 129 & 142°C. These polymers have
exibility. Preliminary degradation results
exibility. Interestingly all these polymers
ld not detect the Tg's. However, DMTA
r.t. as expected due to the ester segments.

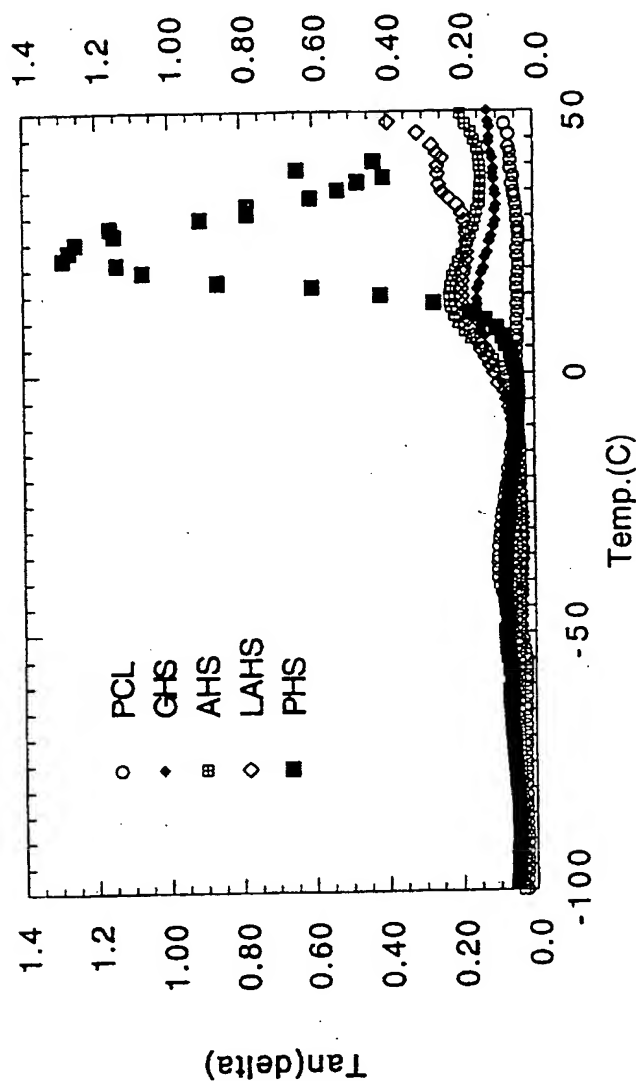


Figure 8. Tan δ vs. Temperature Plots for Poly(amide-ester)s



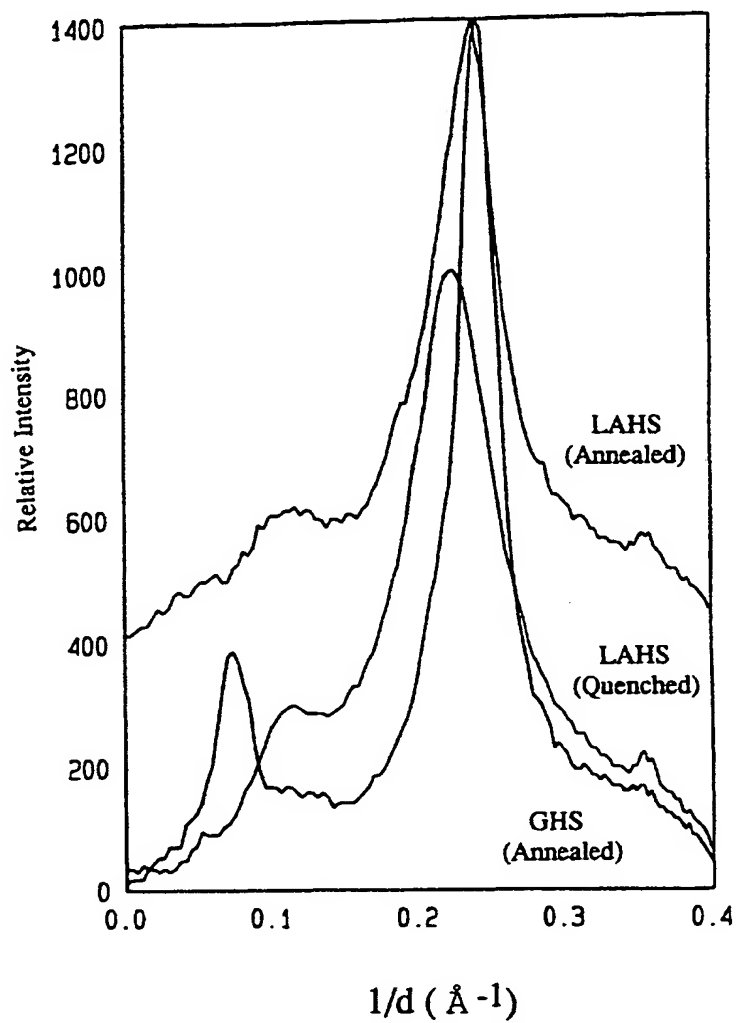


Figure 9. Relative Intensity Profiles of the Small Angle x-Ray Scattering Patterns for LAHS and GHS Polymers

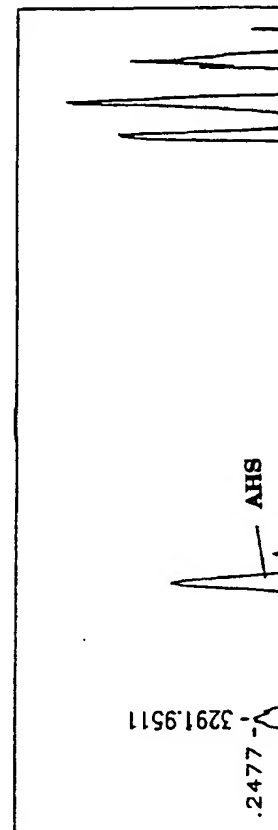

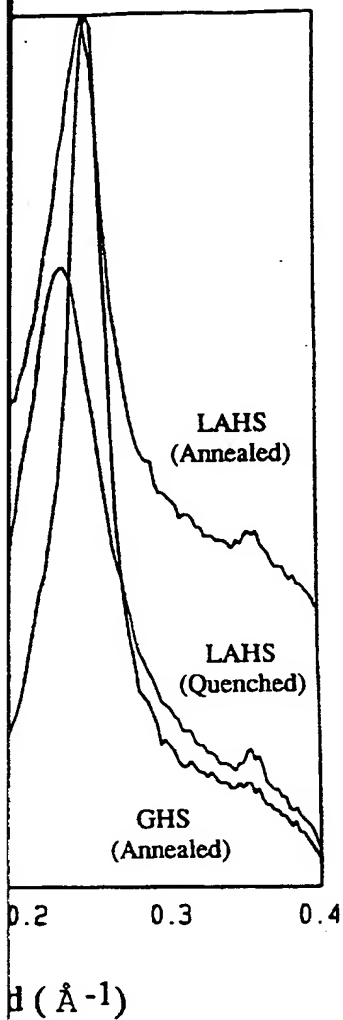

Small Angle x-Ray Scattering
polymers


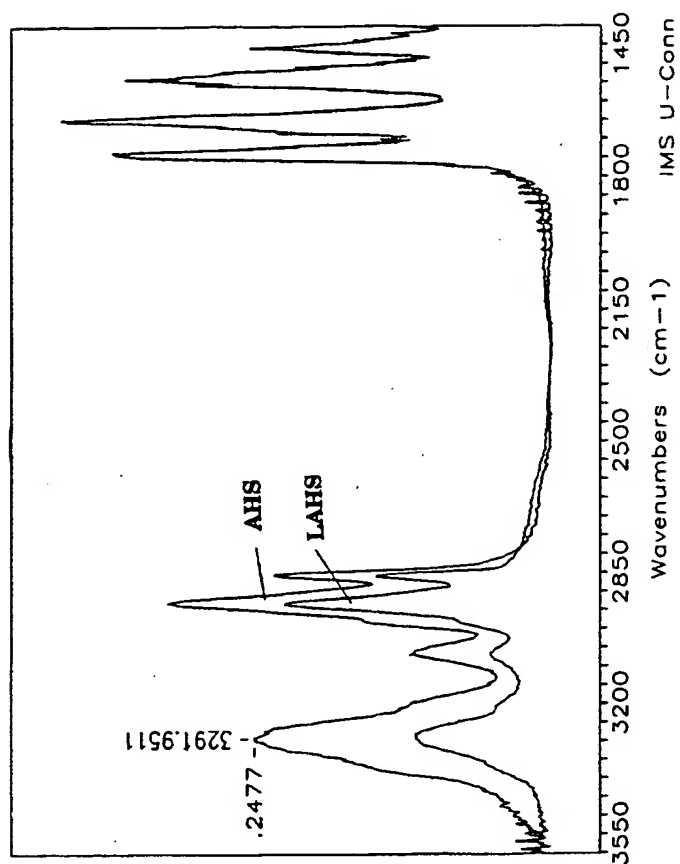


Figure 10. FT-IR Spectra for AHS and LAHS Polymers

Table 2. Summary of the Enzyme Degradation of Poly(amide-ester)s as Measured by Turbidity Measurements.

Polymer	Subtilisin	<i>Fusarium</i>	Lipase	Pronase E	α -Chymotrypsin
PCL(DMF)	1.0	4.0	6.0	0.0	1.3
PCL(THF)	2.0	35.3	0.67	0.0	0.0
GHS	0.0		0.0	0.0	0.0
AHS	12.7		0.7	10.7	5.3
LAHS	8.7	0.0	4.0	32.7	1.3
PHS	0.7		0.7	0.0	0.0
LPHS	3.3		10.7	3.3	13.3
GCHS	0.0		0.0	0.0	0.0
ACHS	1.3	1.3	0.0	2.7	1.3
LACHS	0.0		2.7	1.3	3.3
PCHS	0.0		1.3	2.0	1.3
LPCHS	0.0		6.0	1.3	0.0
GBS	0.0	0.0	1.3	0.0	0.0
ABS	1.3	2.7	0.7	3.3	0.7
LABS	62.7		2.7	28.7	6.7
PBS	4.7	0.0	12.7	0.0	31.3
LPBS	8.0	0.0	14.7	0.0	40.0

Unit = (Δ O.D./min/mg enzyme)*1000

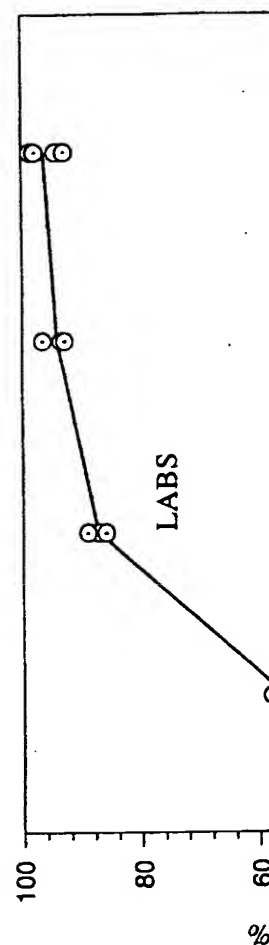

ation of Poly(amide-ester)s
ements.

Pronase E	α -Chymotrypsin
0.0	1.3
0.0	0.0
0.0	0.0
10.7	5.3
32.7	1.3
0.0	0.0
3.3	13.3
0.0	0.0
2.7	1.3
1.3	3.3
2.0	1.3
1.3	0.0
0.0	0.0
3.3	0.7
28.7	6.7
0.0	31.3
0.0	40.0

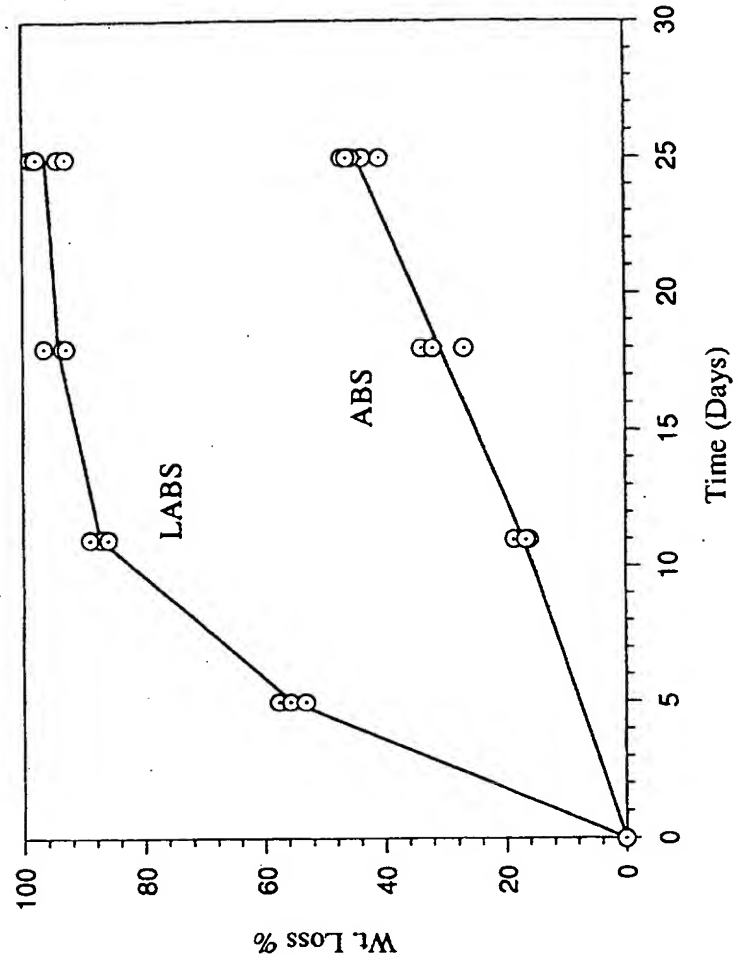



Figure 11. Weight Loss of ABS and LABS Polymers by Pronase E Hydrolysis

Phenylalanine derived polymers are tough materials as indicated by $\tan \delta$, Figure 8. Annealing increases the crystallinity with the optical active monomers derived one better than the one from racemic monomers, as shown by small angle x-ray scattering pattern, Figure 9. It is interesting to note that the "racemic" poly(amide-ester)s have greater extent of H-bonding than the "chiral" poly(amide-esters) as shown by FTIR of LAHS and AHS, Figure 10. This also reflect in higher T_g for the "racemic" polymers than the "chiral" polymers. The arrangement of the structural units in these poly(amide-ester)s are "head-to-head" as compared with "head-to-tail" for poly peptides and poly hydroxycarboxylates, Figure 12. The effect of this on the physical and chemical properties is a subject of our continuing study. As expected, the degradation by enzymes are substituent and chirality specific, Table 2, where semi-qualitative turbidity measurements were used to compare the trends. For example, alpha-chymotrypsin degrades phenylalanine derived PHS and LPHS. This agrees with the result of Eudo et. al.¹¹. Subtilisin and pronase E are active toward poly(amide-ester)s, specially the chiral LAHS, Figure 11.

Experimental

General Characterization Procedures

Fourier Transform Infrared spectra (FT-IR) were recorded on a Nicolet model 60SX spectrophotometer at a resolution of 4 cm^{-1} . Sample preparation involved either casting solution onto KBr disk to form a film, or blending and grounding with KBr powder then pressing into a KBr pellet. Solution FT-IR spectra were recorded between two KBr windows using a rectangular Teflon spacer sandwiched in between. Solvent spectra were used as the background for each spectrum. Sample spectra were then recorded and ratioed against the background. Abbreviations used for FT-IR spectra data are as follow: g=stretching mode; d=bending mode or deformation; max=maximum intensity; Ar=aromatic. Fourier Transform Nuclear Magnetic Resonance spectra (FT-NMR) were recorded on a Bruker AC270 Spectrophotometer. Tetramethylsilane was used as the internal standard. All sample solutions were filtered before measurements to assure homogeneity. Abbreviations used for FT-NMR spectra data are as follow: s=singlet; d=doublet; t=triplet; q=quadruplet; m=multiplet; dd=doublet of doublet. Differential scanning calorimetry (DSC) as performed on a Perkin-Elmer were carried out after samples had been quenched from the melt using a fast cooling rate ($200^\circ\text{C}/\text{min}$). The instrument was calibrated by an indium standard. Solubility

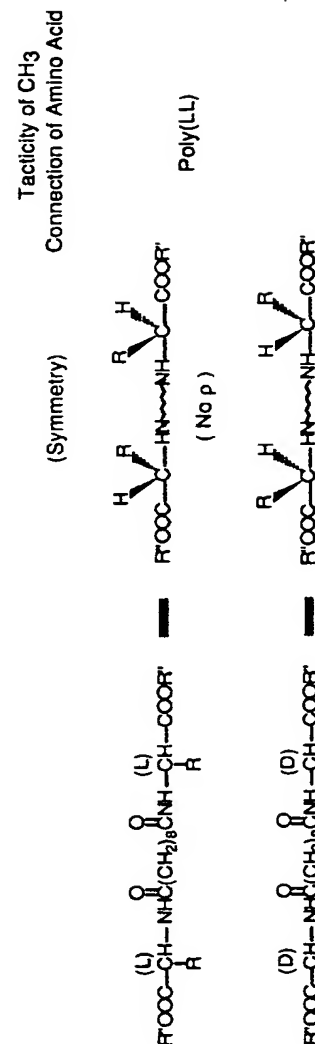

indicated by $\tan \delta$, Figure 8. Annealing
 mers derived one better than the one from
 tering pattern, Figure 9. It is interesting to
 extent of H-bonding than the "chiral" poly
 Figure 10. This also reflect in higher T_g for
 arrangement of the structural units in these
 a "head-to-tail" for poly peptides and poly
 the physical and chemical properties is a
 gradation by enzymes are substituent and
 y measurements were used to compare the
 enylalanine derived PHS and LPHS. This
 pronase E are active toward poly(amide-

recorded on a Nicolet model 60SX
 aration involved either casting solution onto
 with KBr powder, then pressing into a KBr
 vo KBr windows using a rectangular Teflon
 used as the background for each spectrum.
 the background. Abbreviations used for FT-
 ding mode or deformation; max=maximum
 gnetic Resonance spectra (FT-NMR) were
 etramethylsilane was used as the internal
 e measurements to assure homogeneity.
 s follow: s=singlet; d=doublet; t=triplet;
 ifferential scanning calorimetry (DSC) as
 ples had been quenched form the melt using
 brated by and indium standard. Solubility

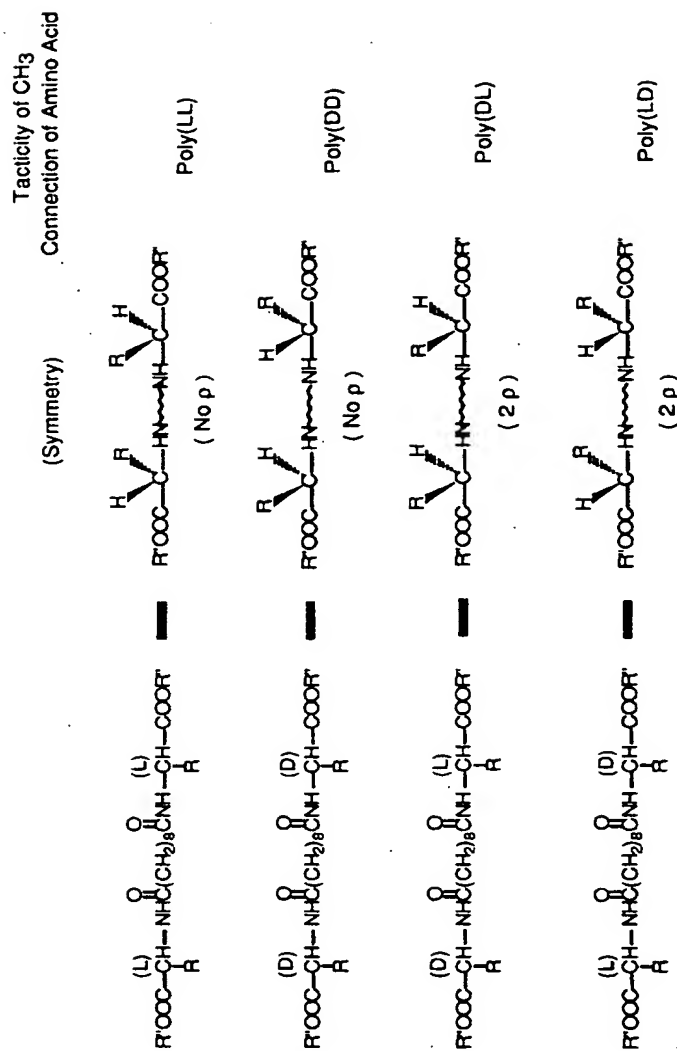


Figure 12. Possible Connections of the Amino Acid Units in Alkyl Bis(DL-amino acid sebacamide)

tests of the polymers were carried out using a concentration of 0.1 w/v (solute/solvent). For samples using low-boiling solvents such as chloroform (CHCl_3), methylene chloride (CH_2Cl_2) and tetrahydrofuran (THF), testing was done at RT. For the tests using high-boiling solvents, such as N,N-dimethylformamide (DMF), they were done both at RT and 70°C. The mixtures of polymer and solvent were heated and maintained at 70°C to determine their solubilities at 70°C. These mixtures were then cooled to RT to determine their solubilities at RT. Dynamic Mechanical Thermal Analysis (DMTA) was performed on a Polymer Laboratories DMTA MKII outfitted with a dual-cantilever head, using a heating rate of 5°C/min. Frequency used was 1 Hz. Samples used for the measurements were compression molded in between two Teflon-coated polyimides films, and quenched in between two cold steel plates. The molding temperatures were 160°C for GHS polymer, 120°C for both AHS and LAHS polymers, and 70°C for PHS polymer. Since AHS, LAHS and PHS polymers had low degree of crystallinity at RT, the soft films obtained from the molding processes were put in between two polyimide films and glass plates with a spacer in between, and annealed at RT for at least 2 weeks before used for DMTA measurements. Small angle x-ray scattering was carried out using Cu-K α radiation ($\lambda=1.54 \text{ \AA}$). The diffraction patterns obtained were transformed into relative intensity profiles. The quenched AHS and LAHS polymers were prepared in a manner similar to those used for the DMTA measurements, without the annealing process. The annealed GHS, AHS and LAHS polymers the same samples but annealed at RT for at least 6 months.

Solvents and Reagents

All chemicals were obtained as reagent grade materials and used as received unless specified. 1,4-butanediol was purified by refluxing, then vacuum-distilling from sodium. Distilled triethylamine was distilled from calcium hydride under an Ar atmosphere. Distilled sebacoyl chloride was obtained by vacuum distillation and kept under Ar before use. Dry methylene chloride and toluene were obtained by refluxing, then distilling from calcium hydride. Activated carbon was obtained from Aldrich Chemical Co. Inc. (cat.#26001-0) and used as received.

Syntheses

All monomers and polymers synthesized and elemental analyses. Details were in

Monomer Synthesis

(A) Amino Acid Diol Diester TsOH Salt

The first type of monomers was synthesized in the presence of toluene and TsOH. The reaction was carried out in a 250 ml bottom flask equipped with an Ar inlet, tube, and a Dean-Stark trap was charged with amino acid (2% in excess relative to the diol) and toluene (c.a. 100 ml per 100 ml of diol). The mixture was stirred and water was distilled out of the mixture. The mixture gradually solidified. Most of the toluene was removed overnight to get either a white or pale yellow solid.

(B) Amino Acid Diol Diesters

This type of monomers was used primarily for solution polymerizations which were carried out in methylene chloride. All the monomers were prepared within a day of their preparation in a procedure as follows. A two liter beaker was charged with anhydrous potassium carbonate (10% in excess relative to the amino acid diol diester TsOH salt), and distilled water was stirred for at least 2 hours. The organic layer was washed twice with methylene chloride, dried over magnesium sulfate, and distilled. At RT overnight, the monomer was obtained as a white solid.

on of 0.1 w/v (solute/solvent). For samples Cl_3), methylene chloride (CH_2Cl_2) and tests using high-boiling solvents, such as at RT and 70°C. The mixtures of polymer determine their solubilities at 70°C. These solubilities at RT. Dynamic Mechanical Laboratories DMTA MKII outfitted with Frequency used was 1 Hz. Samples used were two Teflon-coated polyimides films, molding temperatures were 160°C for GHS 70°C for PHS polymer. Since AHS, LAHS, the soft films obtained from the molding glass plates with a spacer in between, and DMTA measurements. Small angle x-ray (Å). The diffraction patterns obtained were and AHS and LAHS polymers were prepared measurements. without the annealing process. The samples but annealed at RT for at least 6

and used as received unless specified. 1,4-ling from sodium. Distilled triethylamine sphere. Distilled sebacoyl chloride was use. Dry methylene chloride and toluene in hydride. Activated carbon was obtained as received.

Syntheses

All monomers and polymers synthesized were characterized with spectroscopic, molecular weight and elemental analyses. Details were reported elsewhere¹⁵.

Monomer Synthesis

(A) Amino Acid Diol Diester TsOH Salts

The first type of monomers was synthesized from the reaction of various diols and amino acids in the presence of toluene and TsOH. Typical synthetic procedure is as follows. In a 3-neck, round-bottom flask equipped with an Ar inlet, a magnetic stirrer, a condenser with a calcium sulfate drying tube, and a Dean-Stark trap was charged with 1,6-hexanediol or 1,4-*trans*-cyclohexanedimethanol, amino acid (2% in excess relative to the diol), TsOH monohydrate (6% in excess relative to the diol), and toluene (c.a. 100 ml per 100 ml of amino acid). The reaction mixture was refluxed until no more water was distilled out of the mixture. On cooling to RT, the white or pale yellow, viscous liquid gradually solidified. Most of the toluene was decanted and the solid was vacuum dried at 70-100°C overnight to get either a white or pale yellow solid.

(B) Amino Acid Diol Diesters

This type of monomers was used primarily to precisely control the stoichiometric balance needed for solution polymerizations which were carried out by reacting these monomers with sebacoyl chloride in methylene chloride. All the amino acid diol diesters were used to synthesize polymers within a day of their preparation in order to avoid any possible oxidation. Typical synthetic procedure is as follows. A two liter beaker was charged with amino acid diol diester TsOH salt, anhydrous potassium carbonate (10% in excess), methylene chloride (c.a. 2 ml per 1 mmol of amino acid diol diester TsOH salt), and distilled water (same amount as methylene chloride). The mixture was stirred for at least 2 hours. The organic layer was then separated using a separatory funnel. The water layer was washed twice with methylene chloride. All of the methylene chloride layers were combined, dried over magnesium sulfate and then evaporated to dryness. After vacuum drying at RT overnight, the monomer was obtained as a pale yellow liquid.

(C) Alkyl Bis-(amino acid sebacamide)s

This type of monomers was synthesized by interfacial reaction between amino acid alkyl ester hydrochloride in the aqueous phase, containing a weak base, and sebacoyl chloride in methylene chloride. The alkyl group on the amino acid ester was either methyl or ethyl, depending on their availability. A small excess amount of amino acid alkyl ester hydrochloride against the amount of sebacoyl chloride was used to make sure that both acyl chloride groups in the sebacoyl chloride was used to make sure that both acyl chloride groups in the sebacoyl chloride reacted. Similarly, a small excess amount of weak base was used, against the amount of amino acid alkyl ester hydrochloride, to make sure all of the amino acid alkyl ester hydrochloride was freed from the hydrochloride and available for the reaction. Typical synthetic procedure for this type of monomers is as follows. A commercial blender was charged with amino acid alkyl ester hydrochloride (2% in excess relative to sebacoyl chloride) and anhydrous potassium carbonate (2% in excess relative to amino acid alkyl ester hydrochloride). Methylene chloride (c.a. 1.5 ml per 1.00 mmol of alkyl ester hydrochloride) and sebacoyl chloride were then added. Distilled water (same amount as methylene chloride) was added immediately and the blender was stirred at low speed for one to two minutes. The methylene chloride layer was separated. The water layer was then washed twice with small amount of methylene chloride. All of the methylene chloride layers were combined and washed with dilute aqueous potassium carbonate, then distilled water. This interfacial reaction was repeated several times to get enough amounts of monomer. All of the methylene chloride layers from the repeated reactions were combined, dried over magnesium sulfate, then evaporated to dryness to obtain a white or pale yellow powder. Small amount of acid impurities were removed by either treating the powder with activated carbon in hot acetone, filtering, then recrystallizing from acetone/hexanes (glycine and phenylalanine-containing monomers), or by column chromatography using aluminum oxide as the stationary phase and acetone as the moving phase (alanine-containing monomers). After vacuum drying, the monomers were obtained as needle-like crystals (glycine), white powder (DL- and L-alanine) or pale yellow powder (DL- and L-phenylalanine).

Polymer Synthesis**(A) Interfacial Polymerizations**

The following procedure used to synthesize polymerization procedure for the prepolymerization.

Poly(oxyhexamethyleneoxycarbonylmethylenecarbonyliminomethylenecarboxylate)s

In a commercial blender was charged with 1.00 mmol of amino acid alkyl ester hydrochloride, 2.00 mmol of TsOH salt and 2 liters of distilled ice water was added and stirred at low speed for 10 minutes. A mixture of 500 ml of methylene chloride was added. The container used to hold the mixture was rinsed with 100 ml of methylene chloride. The mixture was stirred at low speed for two hours. The reaction was filtered, washed with distilled water. 33.07 g (88%) of white powder.

(B) Solution Polymerizations

The following procedure described for the preparation of all other polymers.

Poly(oxyhexamethyleneoxycarbonylmethylenecarbonylocta-methylenecarboxylate)s

In an Ar-filled glove box, 16.490 g (39.97 mmol) of amino acid alkyl ester hydrochloride was weighed into a 500 ml round bottom flask with 9.559 g (39.97 mmol) of distilled triethylamine. Both flasks were capped, then removed from the glove box. The second flask (8372 mmol) of distilled triethylamine was added to the first flask, then the flask was cooled in an ice bath.

al reaction between amino acid alkyl ester
 base, and sebacyl chloride in methylene
 either methyl or ethyl, depending on their
 ester hydrochloride against the amount of
 chloride groups in the sebacyl chloride was
 sebacyl chloride reacted. Similarly, a small
 amount of amino acid alkyl ester hydrochloride,
 chloride was freed from the hydrochloride ad
 for this type of monomers is as follows. A
 ester hydrochloride (2% in excess relative
 e (2% in excess relative to amino acid alkyl
 er 1.00 mmol of alkyl ester hydrochloride)
 (same amount as methylene chloride) was
 eed for one to two minutes. The methylene
 then washed twice with small amount of
 ers were combined and washed with dilute
 his interfacial reaction was repeated several
 methylene chloride layers from the repeated
 then evaporatd to dryness to obtain a white
 were removed by either treating the powder
 crystallizing from acetone/hexanes (glycine
 chromatography using aluminum oxide as
 anine-containing monomers). After vacuum
 ystals (glycine), white powder (DL-and L-
 ne).

Polymer Synthesis

(A) Interfacial Polymerizations

The following procedure used to synthesize GHS polymer was treated as the standard interfacial polymerization procedure for the preparation of all other polymers synthesized by interfacial polymerization.

Poly(oxyhexamethyleneoxycarbonylmethyleneiminocarbonylocta-methylenecarbonyliminomethylenecarbonyl), GHS

In a commercial blender was charged with 54.5 g (94.5 mmol) of glycine 1,6-hexanediol diester TsOH salt and 2 liters of distilled ice water. 40.9 g of (385.6 mmol) of anhydrous sodium carbonate was added and stirred at low speed for 30 seconds. The mixture turned into a clear solution. A mixture of 500 ml of methylene chloride and 19.35 ml (90.7 mmol) of distilled sebacyl chloride was added. The container used to hold the distilled sebacyl chloride and methylene chloride was rinsed with 100 ml of methylene chloride and the solution was added into the blender. The entire mixture was stirred at low speed for two to three minutes. The solid white powder formed from the reaction was filtered, washed with distilled water, acetone, and then vacuum dried at 80°C to get 33.07 g (88%) of white powder.

(B) Solution Polymerizations

The following procedure described for the preparation of PHS polymer was treated as the standard procedure for the preparation of all other polymers synthesized by solution polymerization.

Poly(oxyhexamethyleneoxycarbonyl-DL-benzylideneiminocarbonylocta-methylenecarbonylocta-methylenecarbonylimino-DL-benzylidenecarbonyl), PHS

In an Ar-filled glove box, 16.490 g (39.97 mmol) of DL-Phenylalanine 1,6-hexanediol diester was weighed into a 500 ml round bottom flask. Another 250 ml round bottom flask was charged with 9.559 g (39.97 mmol) of distilled sebacyl chloride and 80 ml of dry methylene chloride. Both flasks were capped, then removed from the glove box. Under an Ar atmosphere, 11.67 ml (8372 mmol) of distilled triethylamine and 100 ml of dry methylene chloride were added to the first flask, then the flask was cooled in a water bath. The contents of the second flask were added

to the first flask. The second flask was washed with two portions of 10 ml dry methylene chloride and added to the first flask to effect complete transfer of the reagents. All of the transfers and washings were done under an Ar atmosphere. After the reaction mixture was stirred under Ar for 15 hours, it was poured gradually into 1000 ml of boiling water in a 2500 ml beaker. After the precipitation was completed, the water was drained and ice was added. The precipitated polymer was collected as an elastic material from the bottom of the beaker. It was further purified by dissolving in methylene chloride, and washing with water, then precipitating into boiling water. The polymer collected was vacuum dried at 80°C to get a pale yellow, rubber-like material (20.07 g, 87%).

Polymers Synthesized

Poly (oxyhexamethyleneoxycarbonyl-I
DL-ethylidenecarbonyl), AHS

Poly (oxyhexamethyleneoxycarbonyl-I
L-ethylidenecarbonyl), LAHS

Poly(oxyhexamethyleneoxycarbonyl-I
methylenecarbonliminomethylenecarb

Poly (oxymethylene-*trans*-1,4-cyclohe
methyleniminecarbonylocta-methylen

Poly(oxymethylene-*trans*-1,4-cyclohe
ethylideneiminocarbonyloctamethylen

Poly(oxymethylene-*trans*-1,4-cyclohex
ethylideneiminocarbonyloctamethylen

Poly(oxymethylene-*trans*-1,4-cyclohe
benzylideneiminocarbonyloctamethyl

Poly(oxymethylene-*trans*-1,4-cyclohe
benzylideneiminocarbonyloctamethyl

Poly(oxyhexamethyleneoxycarbonyl-I
L-benzylidenecarbonyl), LPHS

portions of 10 ml dry methylene transfer of the reagents. All of the re. After the reaction mixture was stirred 10 ml of boiling water in a 2500 ml beaker. ained and ice was added. The precipitated bottom of the beaker. It was further purified water, then precipitating into boiling water. a pale yellow, rubber-like material (20.07

Polymers Synthesized

Poly (oxyhexamethyleneoxycarbonyl-DL-ethylideneiminocarbonylocta-methylenecarbonylimino-DL-ethylidenecarbonyl), AHS

Poly (oxyhexamethyleneoxycarbonyl-L-ethylideneiminocarbonyloctamethylenecarbonylimino-L-ethylidenecarbonyl), LAHS

Poly(oxyhexamethyleneoxycarbonyl-DL-benzylideneiminocarbonylocta-methylenecarbonliminomethylenecarbonyl), (G-co-P) HS

Poly (oxymethylene-*trans*-1,4-cyclohexylenemethyleneoxycarbonyl-methyleneiminocarbonlocta-methylenecarbonyliminomethylene-carbonyl), GCHS

Poly(oxymethylene-*trans*-1,4-cyclohexylenemethyleneoxy-carbonyl-DL-ethylideneiminocarbonyloctamethylenecarbonylimino-DL-ethylidene-carbonyl) ACHS

Poly(oxmethylene-*trans*-1,4-cyclohexylenemethyleneoxy-carbonyl-L-ethylideneiminocarbonyloctamethylenecarbonylimino-L-ethylidene-carbonyl), LACHS

Poly(oxymethylene-*trans*-1,4-cyclohexylenemethyleneoxy-carbonyl-L-benzylideneiminocarbonyloctamethylenecarbonyliminomethylene-carbonyl), (G-co-LP) CHS

Poly(oxymethylene-*trans*-1,4-cyclohexylenemethyleneoxy-carbonyl-L-benzylideneiminocarbonyloctamethylenecarbonyl-imino-L-benzylidenecarbonyl), LPCHS

Poly(oxyhexamethyleneoxycarbonyl-L-benzylideneiminocarbonylocta-methylenecarbonylimino-L-benzylidenecarbonyl), LPHS

Poly(oxytetramethyleneoxycarbonylmethyleneiminocarbonyloctamethylenecarbonyliminomethylecarbonyl), GBS

Poly(oxymethylene-*trans*-1,4-cyclohexylenemethyleneoxycarbonyl-DL-benzylideneiminocarbonyloctamethylenecarbonyl-imino-DL-benzylidenecarbonyl), PCHS

Poly(oxytetramethyleneoxytrimethyleneiminocarbonyloctamethylenecarbonyliminotrimethylene), Poly(4,9-dioxa-1,12-dodecamethylene sebacamide)

Poly(iminododecamethyleneiminocarbonyloctamethylenecarbonyl), Nylon 12/10

Biodegradation

Methods have been reported elsewhere^{7, 13, 15}.

Conclusion

Potentially very useful biodegradable poly(amide-ester)s of large variety of structure, property and degradability have been prepared from α -amino acids, glycols and dicarboxylic acids.

Acknowledgement

Supports from USDA and Connecticut Critical Technology Research Fund are gratefully acknowledged.

References

1. A.C. Albertsson and S.J. Huang, Issue of J. Macromolecular Sci Marcel Dekker, N.Y.
2. G. Scott and D. Gilead, eds., "Chapman and Hall, London. 19
3. Y. Doi and K. Fukuda, eds., "I Amsterdam, 1994.
4. S.J. Huang, "The Encyclopedia Flemings, and S. Mahajan, eds.
5. S.J. Huang and J.I. Kroschwitz, Engineering", 2nd Ed., John Wi
6. R. Lenz, Advances in Polymer
7. S.J. Huang, D. Bauleban and J.
8. W.J. Bailey, Y. Okamoto, W.C Symp", J.M. Sharpley and A.M p. 765.
9. I. Engleberg and J. Kohn, J. B
10. A. Staubli, E. Ron and R. Lan
11. Y. Saotome, T. Miyazawa and PP. 3-10.
12. L.-H. Ho and S.J. Huang, Poly
13. S.J. Huang, M.S. Roby, C.A. M Plastics", M. Vert. J. Feijen, / Press. Wiltshire, England, 199
14. S.J. Huang, L.-H. Lo, M.T. Hu Plastics and Polymers", Y. Doi 10.

bonylocta-

oxycarbonyl-DL-

o-DL-benzylidenecarbonyl, PCHS

ctamethylenecarbonyiminotrimethylene),

ecarbonyl), Nylon 12/10

s of large variety of structure, property
acids, glycols and dicarboxylic acids.

ogy Research Fund are gratefully

References

1. A.C. Albertsson and S.J. Huang, eds., "Biodegradable Polymers and Recycling", Special Issue of J. Macromolecular Science - Pure and Applied Chemistry, Vol. 32 (4), 1995. Marcel Dekker, N.Y.
2. G. Scott and D. Gilead, eds., "Degradable Polymers: Principles and Applications", Chapman and Hall, London. 1995.
3. Y. Doi and K. Fukuda, eds., "Biodegradable Plastics and Polymers", Elsevier, Amsterdam, 1994.
4. S.J. Huang, "The Encyclopedia of Advanced Materials", D. Bloor, R.J. Brook, M.C. Flemings, and S. Mahajan, eds. Pergamon, 1994, pp. 238-244.
5. S.J. Huang and J.I. Kroschwitz, Ed. 1985. "Mark Encyclopedia of Polymer Science and Engineering", 2nd Ed., John Wiley & Sons, 220:244.
6. R. Lenz, Advances in Polymer Science. 1993, 107, 1.
7. S.J. Huang, D. Bauleban and J.R. Knox, J. Appl. Polym. Sci., 23, 429 (1979).
8. W.J. Bailey, Y. Okamoto, W.C. Kuo, and T. Narita, in "Proc. 3rd Int. Biodegradation Symp", J.M. Sharpley and A.M. Kaplan, eds., Applied Science Publishers, Essex, 1976, p. 765.
9. I. Engleberg and J. Kohn, J. Biomaterials, 12, 292 (1991).
10. A. Staubli, E. Ron and R. Langer, J. Am. Chem. Soc., 112, 4419 (1990).
11. Y. Saotome, T. Miyazawa and T. Endo, Chem. Lett., 21 (1991). Science B.V., 1994, PP. 3-10.
12. L.-H. Ho and S.J. Huang, Polym. Preprints 32(2), 94 (1992).
13. S.J. Huang, M.S. Roby, C.A. Macri and J.A. Cameron, in "Biodegradable Polymers and Plastics", M. Vert. J. Feijen, A.C. Albertsson, G. Scott, and E. Chiellini, eds., Redwood Press. Wiltshire, England, 1992, pp. 149-160.
14. S.J. Huang, L.-H. Lo, M.T. Huang, M.F. Koenig and C.A. Cameron, in "Biodegradable Plastics and Polymers", Y. Doi and K. Fukuda, eds., Elsevier Science B.V., 1994, PP. 3-10.

- ## Inorganic- Biodegrad:

Department of
Park, Pennsylv.

Introduction

Biodegradation, either in the environment or in a laboratory, involves the conversion of a polymeric material by the action of microorganisms. A primary requirement is the ability of the material to be cleaved under enzymic or non-enzymic conditions. The nature of the polymer backbone may also play a part, for example, hydrophilicity or the presence of a functional group that precedes hydrolytic or oxidative cleavage.

Examples of well-known bac
classical organic polymer sy
polyanhydrides, and a range of
polyphosphates, and polyphos
opportunities for the design and

**This Page is Inserted by IFW Indexing and Scanning
Operations and is not part of the Official Record**

BEST AVAILABLE IMAGES

Defective images within this document are accurate representations of the original documents submitted by the applicant.

Defects in the images include but are not limited to the items checked:

- ☒ **BLACK BORDERS**
- ☐ **IMAGE CUT OFF AT TOP, BOTTOM OR SIDES**
- ☒ **FADED TEXT OR DRAWING**
- ☒ **BLURRED OR ILLEGIBLE TEXT OR DRAWING**
- ☐ **SKEWED/SLANTED IMAGES**
- ☐ **COLOR OR BLACK AND WHITE PHOTOGRAPHS**
- ☐ **GRAY SCALE DOCUMENTS**
- ☐ **LINES OR MARKS ON ORIGINAL DOCUMENT**
- ☐ **REFERENCE(S) OR EXHIBIT(S) SUBMITTED ARE POOR QUALITY**
- ☐ **OTHER:** _____

IMAGES ARE BEST AVAILABLE COPY.

As rescanning these documents will not correct the image problems checked, please do not report these problems to the IFW Image Problem Mailbox.

THIS PAGE BLANK (USPTO)